

Advances in Atomic-Scale Frictions with Stick-Slip and Super-Lubricity

Xiang Wang and Scott X Mao*

Department of Mechanical Engineering and Materials Science, University of Pittsburgh, USA

Abstract

With the development of Micro-/Nanoelectromechanical systems (MEMS/NEMS), the friction problems at micro/nanoscale induced the failure of many devices in MEMS. The basic model of atomic-scale friction and associated advancement of experimental research were reviewed in this paper. Two common atomic-friction behaviors, i.e. stick-slip and super-lubricity friction were also discussed here. Challenges and promising points for future research in atomic-scale friction were enumerated.

Keywords

MEMS, Atomic-scale friction, Stick-slip, Super-lubricity

Introduction

Micro-/nanoelectromechanical systems (MEMS/NEMS) are an important part of the integrated circuit industry and MEMS/NEMS devices like accelerators and resonators have been extendedly applied from the aerospace, automobile industry to the biomedical industry [1]. Due to the miniaturization of these devices, numerous tribological phenomena also happen at micro/nanoscale. For instance, as shown in Figure 1, the continuous friction and wear would induce surface damage in MEMS devices. The surface roughness was enhanced by the friction between the silicon sidewall of MEMS device and the on-chip actuator under oscillation, indicated by the circle in Figure 1a [2]. And the friction and wear reduce the lifetime of the microactuators and make the device fail in less than 10^4 cycles [3]. Stiction also could induce the fracture of the freestanding cantilever in a


comb drive (Figure 1b) [4]. Besides, the friction and wear problems are easy to be induced due to the mechanical contact in micro-gears with high-rate rotation [5] and between the rotor and the stator in electrostatic motors [6]. High stiction at the rotor-stator interface limits the operation repeatability in the electrostatic micromotors [7]. The contact-type MEMS switches also require low surface resistance and low friction [8,9]. The strong adhesion or the contact damage directly deteriorate the reliability of the microcontact in MEMS switches [10]. Stiction and wear issues between the yoke and electrode directly influence the operation reliability of micromirror devices [11]. Thus, investigating the friction mechanism is critical to control the damage of devices and improve the feasibility and reliability of MEMS/NEMS like polysilicon microactuators in the magic disk [12], silicon accelerometer in the sensory system [13], polysilicon micro-motors

*Corresponding author: Scott X Mao, Department of Mechanical Engineering and Materials Science, University of Pittsburgh, Pittsburgh, Pennsylvania 15261, USA, Tel: 412-624-9602

Accepted: August 07, 2021; Published: August 09, 2021

Copyright: © 2021 Wang X, et al. This is an open-access article distributed under the terms of the Creative Commons Attribution License, which permits unrestricted use, distribution, and reproduction in any medium, provided the original author and source are credited.

Wang and Mao. *Int J Metall Met Phys* 2021, 6:069



[7], micromirror in the display device [14], and polysilicon micro-gears in the microturbine [15].

Friction between asperities without the participation of any lubricant is called dry friction [16]. In many practical contacts in MEMS devices, no extra lubricant is added and most of the friction problems belong to the dry friction. So, atomic friction research mainly focuses on the dry contact of two asperities. Here, the theoretical model about single-asperity atomic friction was introduced, and then related experimental research about two typical friction behaviors including the stick-slip and superlubricity were reviewed. Finally, some potential points about future research on atomic-scale friction are listed. Investigating atomic friction is expected to provide significant insights to control the friction damage of micro-devices and their feasibility.

The theoretical model of atomic-scale friction

Friction behaviors could be simply classified into two types, stick-slip and super-lubricity in atomic friction [17]. The stick-slip friction behavior could be interpreted well by the classical Prandtl-Tomlinson model proposed in 1920s [18]. The simplest model is for the one-dimensional case and the friction occurs between one tip dragged by a spring and the materials' surface, as shown in Figure 2. The total energy stored in the system could be simplified into [19].

$$U_{tot}(r, t) = U_{eff}(x) + \frac{1}{2}k(x - vt)^2 \quad (1)$$

Where the right first part is an interaction partial

between the tip and surface and the second part is the elastic energy stored in the spring. And the tip located the position x of the minimum U_{tot} and the lateral force could be expressed by [19].

$$F_L = k(x_{tip} - vt) = -\frac{2\pi U_0}{a} \sin \frac{2\pi x_{tip}}{a} \quad (2)$$

and a is the lattice distance between two atoms and k is the effective spring constant [20-22]. Later, the one-dimensional PT model was extended and developed further. The thermal effect and the scanning velocity [23] or the tip shape [24] also could influence the friction force vibration and the PT model was required to be modified.

For example, the atomic friction was simplified as one suspended atom of the tip head sliding on the substrate in the traditional Pt model and thus the needle tip was applied in experiments to investigate the atomic friction [18]. However, in general, the contact surface in real crystal materials has a two-dimension periodicity and the interaction potential between the tip-substrate should be considered into a two-dimension model [25,26].

When loading conditions and friction configuration change, the friction behavior is expected to transit from the stick-slip to smooth sliding with ultralow friction [27-32]. The ultralow friction also is referred to as super-lubricity which was firstly proposed by Hirano, et al. [33] and the friction coefficient of superlubricity is normally in the order of ~ 0.001 [34]. The theory to explain the super-lubricity was known as the "Mechanical Instability" [21,35]. The relation of the interaction potential between the tip-surface and the spring

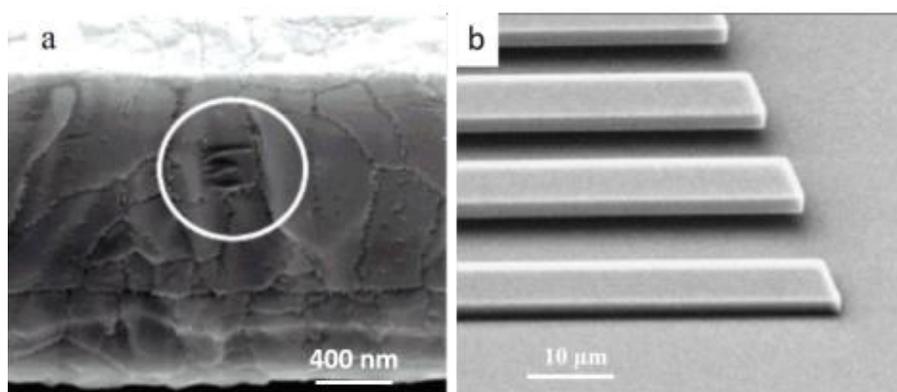


Figure 1: Tribology problems in MEMS/NEMS: a) Damaged surface induced by friction and wear in MEMS devices. The damaged region was marked by the circle. Source: Reprinted with the permission from [2] ©2008 American Chemical Society; b) Stiction-induced fracture of the freestanding cantilever in a comb drive. Source: Reprinted with the permission from [4] ©2002 IOP Publishing.

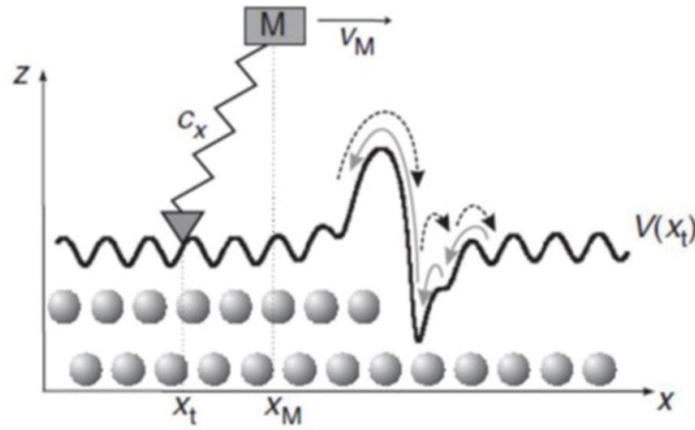


Figure 2: Illustration of The Prandtl-Tomlinson Model. Source: Reprinted with the permission from [22] ©2008 American Physical Society.

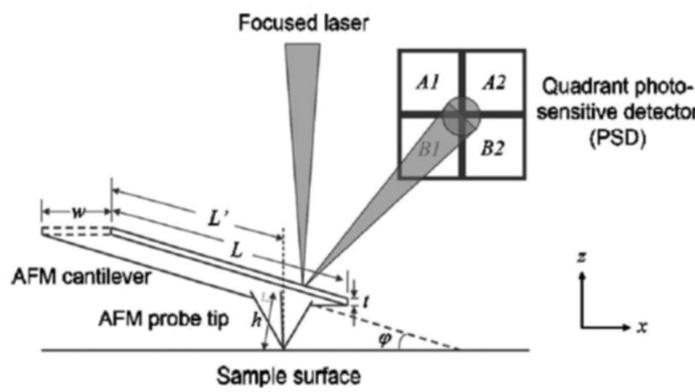


Figure 3: Friction Force Microscopy. Source: Reprinted with the permission from [39] ©2006 AIP Publishing.

stiffness is expressed by a parameter [21,22].

$$\eta = \frac{2\pi^2 U_0}{ka^2} \tag{3}$$

When $\eta > 1$, the model is fitted with stick-slip friction behavior. And for $\eta > 1$, the model could be matched with super-lubricity. The parameter η can be adjusted by changing the normal force [36] and the cantilever stiffness [37] to achieve the reduction of the friction force in experimental observation. Predicted friction behaviors and the transition between stick-slip and superlubricity have been revealed by efforts on the experimental observation.

Atomic-scale friction investigated by AFM-based technology

Generally, the friction coefficient-the ratio of the normal force and the friction force at the dynamic friction stage is used to evaluate the friction between two asperities. The critical issue for friction problems

is to measure the magnitude of the friction force. However, the friction force is very small at micro/nanoscale contact and the force-sensitive tool is required to detect this small force. Based on the concept of atomic force microscopy (AFM), friction force microscopy or lateral force microscopy (Figure 3) has been invented to determine the friction force between a rigid tip and the contact surface [38,39]. The principle to measure the force is to measure the vertical deflection and torsion of the cantilever using sensitive photosensors. With the aid of friction force microscopy, the friction behavior at atomic scale could be revealed and abundant friction researches have been carried out in previous decades [40]. Numerous MEMS devices are fabricated from silicon (Si)-based materials [41]. Zhang, et al. [42] found that the nanoscale friction behaviors are dominated by the nano-sliding with a low friction coefficient between two-body silicon contact when the surface deformation is within the adhering regime. Using friction force microscopy,

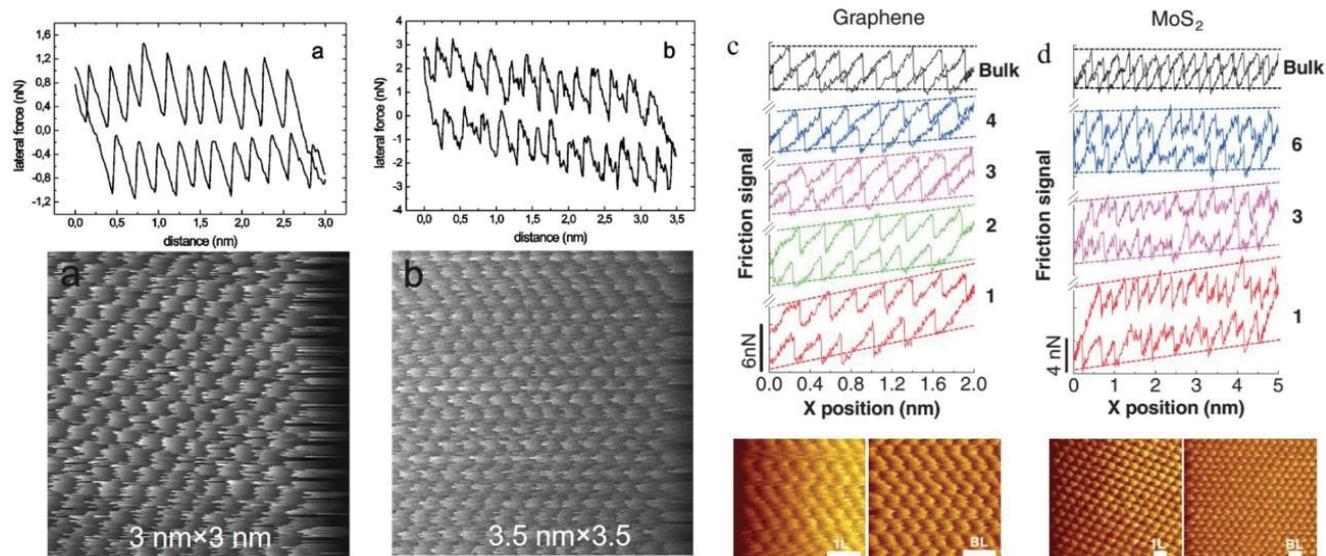


Figure 4: Stick-Slip Friction on Metal Surface and in 2D materials: a,b) The stick-slip friction on the copper (111) surface. Source: Reprinted with the permission from [68] ©1999 American Physical Society; c,d) The stick-slip friction behaviors in Graphene and MoS₂. Source: Reprinted with the permission from [53] ©2006 The American Association for the Advancement of Science.

Schirmeisen, et al. investigated the temperature-related point contact frictional behaviors on silicon wafer and found that the friction exhibits a logarithmic sliding velocity-dependence below 150 K but keeps nearly-constant above 150 K [43]. Later, Marchetto, et al. [44] found that the nano-pattern on silicon surface can effectively lower the friction coefficient and avoid wear in the two-dimensional flat contact of silicon by AFM-based friction tests. Silicon carbide (SiC) is an important substitute material for silicon to be applied in MEMS devices. Zum Gahr, et al. [45] found that the friction coefficient in nanoscale SiC friction is independent of the humidity [46]. Compared to Si, SiC with high hardness exhibits low friction and less wear under low normal loads [47]. But the plastic deformation and wear are supposed to be induced on SiC surface when the normal load increases to the load regime applied in MEMS devices (> 100 nN) [48].

Using friction force microscopy, the atomic-scale stick-slip behavior in the vacuum has been observed in many materials. As shown in Figure 4a and Figure 4b, the lateral force along the (110) direction on Cu (111) surface showed a typical zigzag change with the sliding distance [49]. The probing tip was covered by the native oxide layer to reduce the adhesion effect and chemical reaction between the tip and substrate in the friction experiments [49]. Some Cu

atoms were expected to transfer to the silicon tip and the friction transited to the contact between copper and copper. However, there lacks of a deep understanding of the diffusion phenomenon on the interface. The morphology of copper (111) surface was captured during the scanning of the silicon, which was based on the imaging of AFM. The wavelength (2.5 angstroms) of the stick-slip friction was consistent with the lattice period of the copper along (110) direction on (111) plane (Figure 4a and Figure 4b). Diamond, as a superior wide-bandgap semiconductor material with excellent mechanical properties, has been widely applied in MEMS sensors [50]. The stick-slip was also reported in the friction on diamond surface and the researchers found that the hydrogen-termination treat could effectively reduce the friction magnitude [51]. This stick-slip friction behavior also has been discovered in many two-dimensional (2D) materials [52]. For example, graphene and molybdenum disulfide (MoS₂) exhibited lattice stick-slip friction and friction singles increased with the thinning of 2D material sheets (Figure 4c and Figure 4d) [53]. The number marked in the figure showed the change of the layer number of the sheet. The intrinsic mechanism of the friction-thickness dependence is contributed to the surface deformation of 2D materials. When the thickness decreased, the interaction between the tip and the top raised which induced the buckling of the top surface.

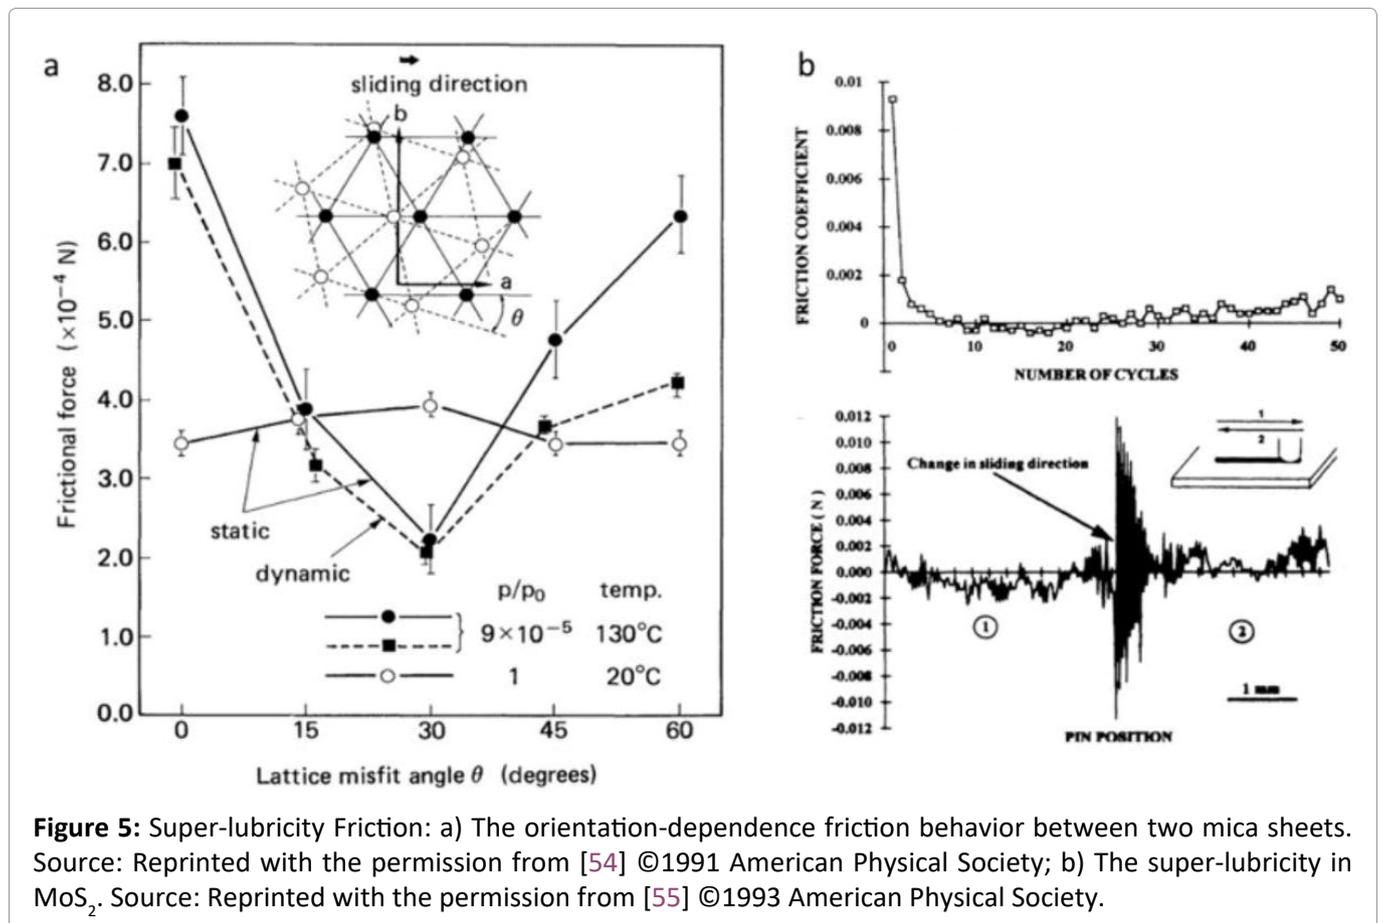


Figure 5: Super-lubricity Friction: a) The orientation-dependence friction behavior between two mica sheets. Source: Reprinted with the permission from [54] ©1991 American Physical Society; b) The super-lubricity in MoS_2 . Source: Reprinted with the permission from [55] ©1993 American Physical Society.

And the sliding of the tip became harder and the energy dissipation increased. The presence of ultralow friction is related to the orientation between two asperities. Hirano, et al. [54] found the orientation-dependence friction behavior between two atomistically-flat mica sheets. The change period of the friction force matched with the lattice symmetry and the ultralow friction force exited when the lattice misorientation was about 30 degrees, as shown in Figure 5a [54]. The super-lubricity also was found in many 2D materials, as shown in Figure 5b [55]. The interaction between the scanning tip and surface is expected to be very weak when the contact occurred at a certain orientation or scanning direction [33]. The superlubricity with friction coefficient ~ 0.003 has been reported in contact between graphene-coated silica nanoparticles and graphene and hexagonal boron nitride substrates [56,57]. Besides, surface-termination/passivation to change the surface properties of materials is a significant approach to lower the friction and achieve superlubricity. Diamond-like carbon (DLC) film with high hardness, as an excellent coating, was applied to improve the frictional properties of devices [58]. Later,

researchers found that the hydrogen termination treatment leading to form the hydrogenated-DLC films could passivate the dangling bonds of carbon atoms and give rise to superlubricity [59,60]. DLC films synthesized from the hydrogenated plasmas vapor deposition could also effectively reduce the friction and lead to superlubricity [61]. The ultralow friction coefficients can be obtained through the passivation of dangling covalent bonds of diamond films favored by oxygen or humid air [62]. If there exists a strong thermal effect during the friction process, the thermal excitations significantly benefit the contact between asperities to overcome the energy barrier of sliding, contributing to a reduction of the friction forces of contacts [63]. The thermal jump rate of the tip could move on the surface with a very low energy barrier. But for strong interaction potential between the tip and surface, the thermal effect becomes weak and the tip motion exhibited the stick-slip behavior again [64]. To achieve superlubricity is imperative to lower the energy dissipation and extend the service life of devices. Superlubricity with ultralow friction has been realized in potential devices of nanoelectromechanical systems (NEMS) by experimental research such as ultralow-friction

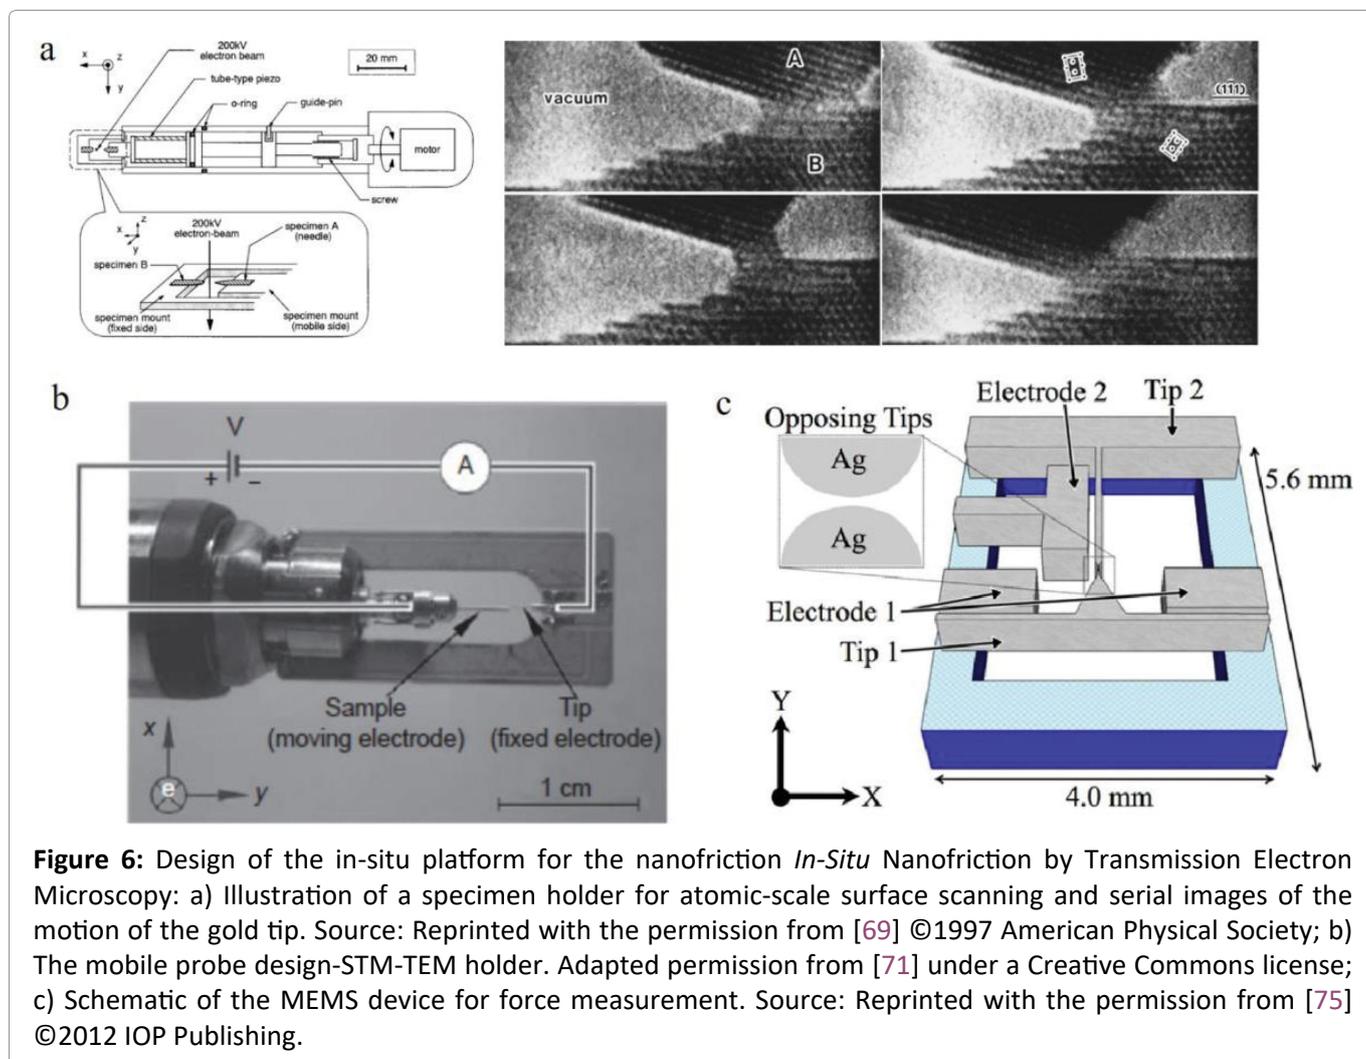


Figure 6: Design of the in-situ platform for the nanofriction *In-Situ* Nanofriction by Transmission Electron Microscopy: a) Illustration of a specimen holder for atomic-scale surface scanning and serial images of the motion of the gold tip. Source: Reprinted with the permission from [69] ©1997 American Physical Society; b) The mobile probe design-STM-TEM holder. Adapted permission from [71] under a Creative Commons license; c) Schematic of the MEMS device for force measurement. Source: Reprinted with the permission from [75] ©2012 IOP Publishing.


nanoscale linear bearings formed by multiwall carbon nanotubes [65], tunable nanoresonators constructed by telescoping nanotubes [66], and nanoscale rotational actuator incorporating a metal plate with carbon nanotubes [67].

***In-situ* TEM observation on atomic-scale friction**

However, the structure characteristic of the friction surface could only be captured by AFM imaging and the real structure evolution of two asperities cannot be revealed by friction force microscopy. Transmission electron microscopy (TEM) provides a window to capture the structure change of friction asperities and record the real-time friction process. How to achieve investing the friction under TEM observation is still a challenge for atomic-friction research, which depends on the development of in-situ TEM techniques. For example, a movable probe was successfully designed in the TEM holder and the motion of the probe was controlled by a low-velocity motor

(Figure 6a) [68]. The minimum step of the probe's motion along the sliding direction is 0.16 nm and the time resolution of the video is 1/60 s [68]. The real-time evolution of the cross-section of Au junction could be recorded by this technique [68]. However, the motion of the probe is confined in one direction and the relative motion between two asperities is hard to carry out. Based on the similar principle of scanning tunneling microscopy, a more flexible control [69] was designed to activate the probe movable (Figure 6b) [70] in three dimensions and the friction between two asperities could be realized [69,71].

Although the friction phenomenon has been recorded by in-situ TEM imaging, the force evolution is still required to be measured by an extra force detection system. AFM is a powerful tool to measure the small force and implanting AFM cantilever into TEM [72] provides an ideal method to evaluate the force at atomic-scale (Figure 6c) [73]. A similar system with two force sensors was

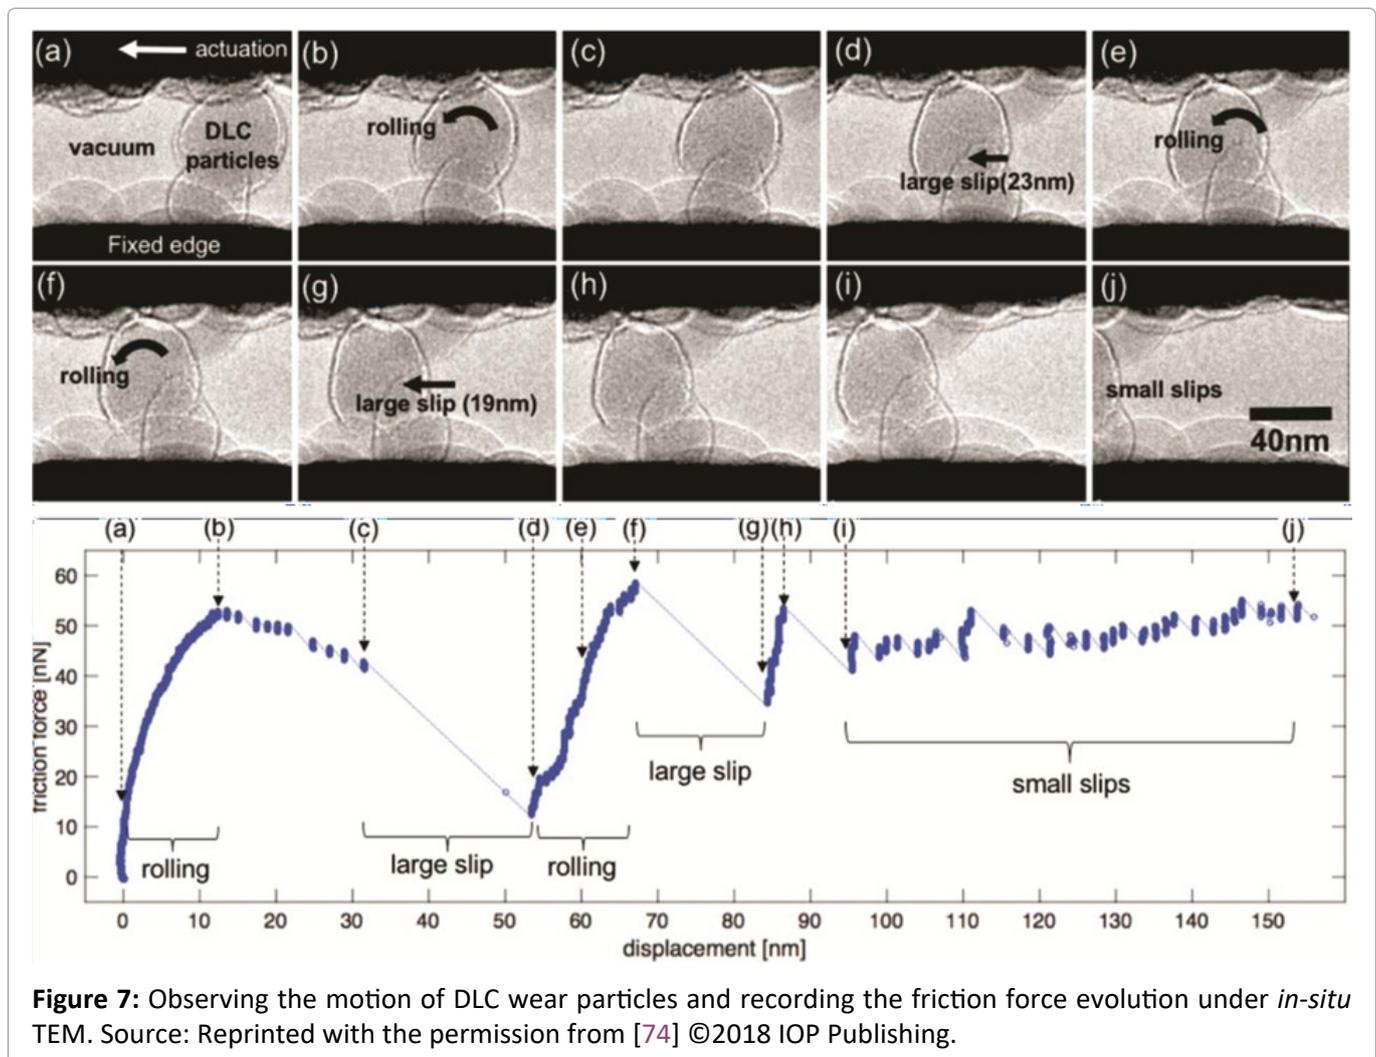

invented to measure the friction and normal force at the same time during the TEM observation [74]. The speed of the probe is about 10 nm min^{-1} [74]. For example, the simultaneous change of the friction force between two silicon surfaces covered with diamond-like carbon (DLC) (Figure 7) was captured by the developed MEMS devices under *in-situ* TEM [74]. There existed three main mechanical behaviors including the rolling, the slipping, and the sticking of particles between the contacting surfaces were successfully captured and the movement of the wear particle mediated the friction process [73]. The detection precision about the force reaches the level of nN and the movement velocity of the probe can be adjusted within $1\text{-}500 \text{ nm s}^{-1}$ [73]. These *in-situ* researches under TEM observation focus on the plastic deformation of asperity like the formation and fracture of the neck between asperities [74,75] or wear [76]. However, the atomic-scale observation about the well-defined interface structure, directly affecting the frictional behaviors has not been acquired. Some pioneer

experiments have revealed the surface defects like the step has significant effects on friction [22] but the real-time evolution on the interface and the dynamic interaction between the sliding probe and the surface step has not been visualized.

Summary and Outlook

The P-T model provides a simple theory to understand the atomic friction and the developed model can be applied to explain two typical atomic-friction behaviors, i.e. the stick-slip and superlubricity. They have been reported by much experimental research through AFM-based technology. The transition between these two behaviors can be explained by the parameter η which can be adjusted by changing the friction configuration and loading conditions. Furthermore, advanced *in-situ* TEM provides new opportunities to investigate the contact evolution during friction and the relations between the interface and friction force evolutions can be built up by combining the force-measurement system under

TEM observation. However, some challenges and key points, which are of potential interest for future research in atomic-scale friction, are required with much attention to be overcome.

- The real-time atomic-scale observation on the interface between asperities is still a challenge for friction research, and smart methods especially for in-situ high-resolution TEM technologies, are expected to be proposed.
- Lowering the drift effect [77] and improving the accuracy of force measurement [78] are significant to extend the in-situ technologies for future atomic-scale friction research.
- It is well-known that the materials' properties may experience huge transition when the size of the asperities reduces to nanoscale or even smaller [79,80]. Multiple technologies will be required to characterize the complex interface phenomenon such as sliding-induced diffusion or segregation [81] in alloy systems in atomic-scale friction.
- Extending the revealed friction mechanism at atomic-scale to macroscopic application demands the future advancement of the theoretical model and experimental designs considering the practical environment in friction systems.

Acknowledgments

S. X. M. acknowledges support from National Science Foundation (NSF CMMI 1824816) through University of Pittsburgh.

References

1. Pattanaik P, Ojha M (2021) Review on challenges in MEMS technology. *Materials Today: Proceedings*.
2. Asay DB, Dugger MT, Ohlhausen JA, Kim SH (2008) Macro-to nanoscale wear prevention via molecular adsorption. *Langmuir* 24: 155-159.
3. Patton ST, Zabinski JS (2002) Failure mechanisms of a MEMS actuator in very high vacuum. *Tribology International* 35: 373-379.
4. Van Spengen WM, Puers R, De Wolf I (2002) A physical model to predict stiction in MEMS. *Journal of Micromechanics and Microengineering* 12: 702.
5. Bhushan B (2005) Plenary lecture 1st Vienna conference.
6. Lafontan X, Presseccq F, Beaudoin F, Rigo S, Dardalhon M, et al. (2003) The advent of MEMS in space. *Microelectronics Reliability* 43: 1061-1083.
7. Tai YC, Fan LS, Muller RS (1989) IC-processed micro-motors: Design, technology, and testing. *IEEE Micro Electro Mechanical Systems*, 1-6.
8. Majumder S, McGruer N, Adams G (2005) Adhesion and contact resistance in an electrostatic MEMS microswitch. *18th IEEE International Conference on Micro Electro Mechanical Systems*, 215-218.
9. McGruer N, Adams G, Chen L, Guo Z, Du Y (2006) Mechanical, thermal, and material influences on ohmic-contact-type MEMS switch operation. *19th IEEE International Conference on Micro Electro Mechanical Systems*, 230-233.
10. Basu A, Adams G, McGruer N (2016) A review of micro-contact physics, materials, and failure mechanisms in direct-contact RF MEMS switches. *Journal of Micromechanics and Microengineering* 26: 104004.
11. Henck SA (1997) Lubrication of digital micromirror-devices TM. *Tribology Letters* 3: 239-247.
12. Horsley DA, Cohn MB, Singh A, Horowitz R, Pisano AP (1998) Design and fabrication of an angular microactuator for magnetic disk drives. *Journal of Microelectromechanical Systems* 7: 141-148.
13. Sulouff R (1998) MEMS opportunities in accelerometers and gyros and the microtribology problems limiting commercialization. *Tribology Issues and opportunities in MEMS*, 109-120.
14. Hornbeck LJ (1999) Digital light processing update: Status and future applications. *International Society for Optics and Photonics* 3634: 158-170.
15. Mehregany M, Gabriel KJ, Trimmer WS (1988) Integrated fabrication of polysilicon mechanisms. *IEEE Transactions on Electron Devices* 35: 719-723.
16. Feeny B, Guran AS, Hinrichs N, Popp K (1998) A historical review on dry friction and stick-slip phenomena. *Applied Mechanics Reviews* 51: 321-341.
17. Bhushan B (2008) *Nanotribology and nanomechanics: An introduction*. Springer Science & Business Media.
18. Tomlinson GA (1929) CVI. A molecular theory of friction. *The London, Edinburgh, and Dublin Philosophical Magazine and Journal of Science* 7: 905-939.
19. Gnecco E, Meyer E (2015) Fundamentals of friction and wear on the nanoscale. *Nanoscience and Technology, Springer*, 517-543.
20. Lantz M, O'shea S, Hoole A, Welland M (1997) Lateral stiffness of the tip and tip-sample contact in frictional

- force microscopy. *Appl Phys Lett* 70: 970-972.
21. Hölscher H, Schirmeisen A, Schwarz UD (2008) Principles of atomic friction: From sticking atoms to superlubric sliding. *Philos Trans A Math Phys Eng Sci* 366: 1383-1404.
 22. Hölscher H, Ebeling D, Schwarz UD (2008) Friction at atomic-scale surface steps: Experiment and theory. *Phys Rev Lett* 101: 246105.
 23. Gnecco E, Bennewitz R, Gyalog T, Loppacher C, Bammerlin M, et al. (2000) Velocity dependence of atomic friction. *Phys Rev Lett* 84: 1172-1175.
 24. Ye Z, Otero-de-la-Roza A, Johnson ER, Martini A (2013) Effect of tip shape on atomic-friction at graphite step edges. *Appl Phys Lett* 103: 081601.
 25. Steiner P, Roth R, Gnecco E, Baratoff A, Maier S, et al. (2009) Two-dimensional simulation of superlubricity on NaCl and highly oriented pyrolytic graphite. *Physical Review B* 79: 045414.
 26. Dong Y, Vadakkepatt A, Martini A (2011) Analytical models for atomic friction. *Tribology Letters* 44: 367.
 27. Braun OM, Röder J (2002) Transition from stick-slip to smooth sliding: An earthquakelike model. *Phy Rev Lett* 88: 096102.
 28. Gourdon D, Israelachvili JN (2003) Transitions between smooth and complex stick-slip sliding of surfaces. *Phys Rev E* 68: 021602.
 29. Socoliuc A, Bennewitz R, Gnecco E, Meyer E (2004) Transition from stick-slip to continuous sliding in atomic friction: entering a new regime of ultralow friction. *Phys Rev Lett* 92: 134301.
 30. Braun O, Peyrard M, Bortolani V, Franchini A, Vanossi A (2005) Transition from smooth sliding to stick-slip motion in a single frictional contact. *Phys Rev E Stat Nonlin Soft Matter Phys* 72: 056116.
 31. Socoliuc A, Gnecco E, Maier S, Pfeiffer O, Baratoff A, et al. (2006) Atomic-scale control of friction by actuation of nanometer-sized contacts. *Science* 313: 207-210.
 32. Breki A, Nosonovsky M (2018) Ultraslow frictional sliding and the stick-slip transition. *Applied Physics Letters* 113: 241602.
 33. Hirano M, Shinjo K (1990) Atomistic locking and friction. *Phys Rev B Condens Matter* 41: 11837-11851.
 34. Martin JM, Erdemir A (2018) Superlubricity: Friction's vanishing act. *Physics Today* 71: 40.
 35. Hirano M (2003) Superlubricity: A state of vanishing friction. *Wear* 254: 932-940.
 36. Gosvami NN, Filleter T, Egberts P, Bennewitz R (2010) Microscopic friction studies on metal surfaces. *Tribology letters* 39: 19-24.
 37. Wang ZJ, Ma TB, Hu YZ, Xu L, Wang H (2015) Energy dissipation of atomic-scale friction based on one-dimensional Prandtl-Tomlinson model. *Friction* 3: 170-182.
 38. Liu E, Blanpain B, Celis JP (1996) Calibration procedures for frictional measurements with a lateral force microscope. *Wear* 192: 141-150.
 39. Cannara RJ, Eglin M, Carpick RW (2006) Lateral force calibration in atomic force microscopy: A new lateral force calibration method and general guidelines for optimization. *Review of Scientific Instruments* 77: 053701.
 40. Bhushan B (2011) *Nanotribology and nanomechanics I: Measurement techniques and nanomechanics*. Science & Business Media, Springer.
 41. Fischer AC, Forsberg F, Lapisa M, Bleiker SJ, Stemme G, et al. (2015) Integrating MEMS and ICs. *Microsystems & Nanoengineering* 1: 1-16.
 42. Zhang L, Tanaka H (1998) Atomic scale deformation in silicon monocrystals induced by two-body and three-body contact sliding. *Tribology international* 31: 425-433.
 43. Schirmeisen A, Jansen L, Hölscher H, Fuchs H (2006) Temperature dependence of point contact friction on silicon. *Applied Physics Letters* 88: 123108.
 44. Marchetto D, Rota A, Calabri L, Gazzadi GC, Menozzi C, et al. (2008) AFM investigation of tribological properties of nano-patterned silicon surface. *Wear* 265: 577-582.
 45. Jiang L, Cheung R (2009) A review of silicon carbide development in MEMS applications. *Int J Computational Materials Science and Surface Engineering* 2: 227-242.
 46. Zum Gahr KH, Blattner R, Hwang DH, Pöhlmann K (2001) Micro-and macro-tribological properties of SiC ceramics in sliding contact. *Wear* 250: 299-310.
 47. Sundararajan S, Bhushan B (1998) Micro/nanotribological studies of polysilicon and SiC films for MEMS applications. *Wear* 217: 251-261.
 48. Tangpatjaroen C, Grierson D, Shannon S, Jakes JE, Szlufarska I (2017) Size dependence of nanoscale wear of silicon carbide. *ACS Appl Mater Interfaces* 9: 1929-1940.
 49. Bennewitz R, Gyalog T, Guggisberg M, Bammerlin M, Meyer E, et al. (1999) Atomic-scale stick-slip processes on Cu(111). *Phys Rev B* 60: 11301-11304.

50. Liao M (2021) Progress in semiconductor diamond photodetectors and MEMS sensors. *Functional Diamond* 1: 29-46.
51. Van den Oetelaar RJA, Flipse CFJ (1997) Atomic-scale friction on diamond (111) studied by ultra-high vacuum atomic force microscopy. *Surface Science* 384: 828-835.
52. Zhang S, Ma T, Erdemir A, Li Q (2019) Tribology of two-dimensional materials: From mechanisms to modulating strategies. *Materials Today* 26: 67-86.
53. Lee C, Li Q, Kalb W, Liu XZ, Berger H, et al. (2010) Frictional characteristics of atomically thin sheets. *Science* 328: 76-80.
54. Hirano M, Shinjo K, Kaneko R, Murata Y (1991) Anisotropy of frictional forces in muscovite mica. *Phys Rev Lett* 67: 2642-2645.
55. Martin JM, Donnet C, Le Mogne T, Epicier T (1993) Superlubricity of molybdenum disulphide. *Phys Rev B Condens Matter* 48: 10583-10586.
56. Liu Z, Yang J, Grey F, Liu JZ, Liu Y, et al. (2012) Observation of microscale superlubricity in graphite. *Phys Rev Lett* 108: 205503.
57. Liu SW, Wang HP, Xu Q, Ma TB, Yu G, et al. (2017) Robust microscale superlubricity under high contact pressure enabled by graphene-coated microsphere. *Nat Commun* 8: 14029.
58. Kano M (2006) DLC coating technology applied to sliding parts of automotive engine. *New Diamond and Frontier Carbon Technology* 16: 201-210.
59. Erdemir A, Eryilmaz O, Fenske G (2000) Synthesis of diamondlike carbon films with superlow friction and wear properties. *Journal of Vacuum Science & Technology A: Vacuum, Surfaces, and Films* 18: 1987-1992.
60. Morita Y, Shibata T, Onodera T, Sahnoun R, Koyama M, et al. (2008) Effect of surface termination on superlow friction of diamond film: A theoretical study. *Japanese Journal of Applied Physics* 47: 3032-3035.
61. Erdemir A, Eryilmaz O (2014) Achieving superlubricity in DLC films by controlling bulk, surface, and tribochemistry. *Friction* 2: 140-155.
62. Kumar N, Sharma N, Dash S, Popov C, Kulisch W, et al. (2011) Tribological properties of ultrananocrystalline diamond films in various test atmosphere. *Tribology International* 44: 2042-2049.
63. Krylov SY, Jinesh K, Valk H, Dienwiebel M, Frenken J (2005) Thermally induced suppression of friction at the atomic scale. *Phys Rev E Stat Nonlin Soft Matter Phys* 71: 065101.
64. Krylov SY, Frenken JW (2007) Thermal contact delocalization in atomic scale friction: a multitude of friction regimes. *New Journal of Physics* 9: 398.
65. Cumings J, Zettl A (2000) Low-friction nanoscale linear bearing realized from multiwall carbon nanotubes. *Science* 289: 602-604.
66. Jensen K, Girit C, Mickelson W, Zettl A (2006) Tunable nanoresonators constructed from telescoping nanotubes. *Phys Rev Lett* 96: 215503.
67. Fennimore AM, Yuzvinsky TD, Han WQ, Fuhrer MS, Cumings J, et al. (2003) Rotational actuators based on carbon nanotubes. *Nature* 424: 408-410.
68. Kizuka T, Yamada K, Deguchi S, Naruse M, Tanaka N (1997) Cross-sectional time-resolved high-resolution transmission electron microscopy of atomic-scale contact and noncontact-type scanings on gold surfaces. *Phys Rev B* 55: 7398.
69. Nafari A, Karlen D, Rusu C, Svensson K, Olin H, et al. (2008) MEMS sensor for in situ TEM atomic force microscopy. *Journal of Microelectromechanical Systems* 17: 328-333.
70. Golberg D, Costa PM, Mitome M, Bando Y (2008) Nanotubes in a gradient electric field as revealed by STM TEM technique. *Nano Research* 1: 166-175.
71. M'ndange-Pfupfu A, Ciston J, Eryilmaz O, Erdemir A, Marks L (2013) Direct observation of tribochemically assisted wear on diamond-like carbon thin films. *Tribol Lett* 49: 351-356.
72. Jacobs TD, Carpick RW (2013) Nanoscale wear as a stress-assisted chemical reaction. *Nat Nanotechnol* 8: 108-112.
73. Sato T, Nabeya S, Menon V, Ishida T, Kometani R, et al. (2018) Real-time observation of slipping and rolling events in DLC wear nanoparticles. *Nanotechnology* 29: 325707.
74. Sato T, Ishida T, Jalabert L, Fujita H (2012) Real-time transmission electron microscope observation of nanofriction at a single Ag asperity. *Nanotechnology* 23: 505701.
75. Ishida T, Sato T, Ishikawa T, Oguma M, Itamura N, et al. (2015) Time-lapse nanoscopy of friction in the non-amontons and non-coulomb regime. *Nano Letters* 15: 1476-1480.
76. Liao Y, Marks L (2017) In situ single asperity wear at the nanometre scale. *International Materials Reviews* 62: 99-115.
77. Taheri ML, Stach EA, Arslan I, Crozier PA, Kabius BC, et al. (2016) Current status and future directions for in situ transmission electron microscopy. *Ultramicroscopy* 170: 86-95.

78. Stierstedt J, Rutland MW, Attard P (2005) A novel technique for the in situ calibration and measurement of friction with the atomic force microscope. *Review of Scientific Instruments* 76: 083710.
79. Zhu TT, Bushby AJ, Dunstan DJ (2008) Materials mechanical size effects: A review. *Materials Technology* 23: 193-209.
80. Greer JR, De Hosson JTM (2011) Plasticity in small-sized metallic systems: Intrinsic versus extrinsic size effect. *Progress in Materials Science* 56: 654-724.
81. Tarasov SY, Filippov A, Kolubaev E, Kalashnikova T (2017) Adhesion transfer in sliding a steel ball against an aluminum alloy. *Tribology International* 115: 191-198.

